

# **A Low-Cost Approach to Fabrication of Multinary Compounds for Energy-Related Applications**

**Preprint**

R.N. Bhattacharya and S.K. Deb

*To Be Presented at the 12<sup>th</sup> International Conference in  
Ternary and Multinary Compounds  
Hsin-chu, Taiwan  
March 13-17, 2000*



**NREL**

**National Renewable Energy Laboratory**

1617 Cole Boulevard  
Golden, Colorado 80401-3393

NREL is a U.S. Department of Energy Laboratory  
Operated by Midwest Research Institute • Battelle • Bechtel

Contract No. DE-AC36-99-GO10337

## NOTICE

The submitted manuscript has been offered by an employee of the Midwest Research Institute (MRI), a contractor of the US Government under Contract No. DE-AC36-99GO10337. Accordingly, the US Government and MRI retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.doe.gov/bridge>

Available for a processing fee to U.S. Department of Energy  
and its contractors, in paper, from:

U.S. Department of Energy  
Office of Scientific and Technical Information  
P.O. Box 62  
Oak Ridge, TN 37831-0062  
phone: 865.576.8401  
fax: 865.576.5728  
email: [reports@adonis.osti.gov](mailto:reports@adonis.osti.gov)

Available for sale to the public, in paper, from:

U.S. Department of Commerce  
National Technical Information Service  
5285 Port Royal Road  
Springfield, VA 22161  
phone: 800.553.6847  
fax: 703.605.6900  
email: [orders@ntis.fedworld.gov](mailto:orders@ntis.fedworld.gov)  
online ordering: <http://www.ntis.gov/ordering.htm>



Printed on paper containing at least 50% wastepaper, including 20% postconsumer waste

# A Low-Cost Approach to Fabrication of Multinary Compounds for Energy-Related Applications

Raghu N. BHATTACHARYA and Satyen K. DEB

National Renewable Energy Laboratory  
1617 Cole Boulevard, Golden, CO 80401

Non-vacuum electrodeposition and electroless deposition techniques with a potential to prepare large-area uniform precursor films using low-cost source materials and low-cost capital equipment are very attractive for the growth of compound materials for superconductors and photovoltaic applications. In the first part, a low-cost electrodeposition (ED) method will be discussed for fabrication of high-temperature Tl-oxide-based superconductors. In the second part, electrodeposition and electroless deposition of semiconductor Cu-In-Ga-Se thin films will be discussed.

KEYWORDS: low-cost fabrication; multinary compounds; electrodeposition, electroless deposition; superconductors; photovoltaics

Non-vacuum electrodeposition and electroless deposition techniques with a potential to prepare large-area uniform precursor films using low-cost source materials and low-cost capital equipment are very attractive for the growth of compound materials for superconductors and photovoltaic applications.

In the first part of the paper, a low-cost electrodeposition (ED) method will be discussed for fabricating high-temperature Tl-oxide-based superconductors. The primary technical challenge that must be satisfied to permit high-temperature superconductor (HTS) wire or tape in superconducting magnets or power-related applications is the successful demonstration of a low-cost, high-field, high-current-carrying wire or tape with acceptable mechanical properties ( $>10^5$  A/cm<sup>2</sup> at 77 K in magnetic fields of  $>0.2$  T). The Tl-based superconducting oxides are excellent candidates because of their high transition temperatures reaching to 127 K and unique features in their growth morphology. Research on the single-layer Tl-1223 compound, with Pb, Bi, and Sr substitution for the Tl and Ba, respectively, has recently received more attention due to the promise of improved transport behavior in magnetic field and phase stability competitive with the YBa<sub>2</sub>Cu<sub>3</sub>O<sub>x</sub> (YBCO) compound at 77 K operating temperature.<sup>1,2</sup> Electrodeposited (Tl,Bi)-(Sr,Ba)-Ca-Cu-Ag (TBSBCCO) thick-film wire or tape has considerable practical potential for fabricating a low-cost, high-field, high-current-carrying conductor suitable for superconducting magnets or power-

related applications. A multi-cation thick coating of 1-5  $\mu$ m can be electrodeposited easily at the desired stoichiometry from an electrolyte solution onto a conducting substrate. At present, we are optimizing a low-cost, commercially scalable ED processing to demonstrate biaxially textured Tl-1223 with Bi and Sr substitution on single-crystal substrates that will be transitioned to the flexible textured Ni.<sup>3</sup> The single-crystal results will establish a base-line reference and proof of principle for transition to a suitably buffered metallic substrate. The electrodeposited superconductor precursor films were obtained by co-electrodeposition of the constituent metals using nitrate salts dissolved in dimethyl sulfoxide (DMSO) solvent. The electrodeposition was performed in a closed-cell configuration at 24°C. A number of electrodeposition runs were performed with different electrolyte compositions, and the precursor films were analyzed by inductively coupled plasma (ICP) spectrometry to establish the stoichiometry of the deposited elements. The cation ratios of the electrodeposition bath were adjusted systematically to obtain (TlBi)<sub>0.9</sub>Sr<sub>1.6</sub>Ba<sub>0.4</sub>Ca<sub>2</sub>Cu<sub>3</sub>Ag<sub>0.2</sub> (TBSBCCO-Ag) precursor compositions. A typical electrolyte bath composition for the TBSBCCO-Ag films consisted of 0.018 M TlNO<sub>3</sub>, 0.009 M Bi(NO<sub>3</sub>)<sub>3</sub>·5H<sub>2</sub>O, 0.297 M Sr(NO<sub>3</sub>)<sub>2</sub>, 0.212 M Cu(NO<sub>3</sub>)<sub>2</sub>·6H<sub>2</sub>O, and 0.002 M AgNO<sub>3</sub> dissolved in dimethyl sulfoxide solvent. The films were electroplated by using constant potential at -3 V. Pole-figure measurements of electrodeposited (TBSBCCO) films, with thicknesses between 1-5  $\mu$ m, clearly show strong biaxial texturing. The rocking curve and phi scan of TBSBCCO on 300-Å Ag/LaAlO<sub>3</sub> show a full-width half-maximum (FWHM) of only 0.52° and 0.5°, respectively, consistent with a very high-quality film. Transport measurements for the ED films show critical current density  $J_c$  values above  $10^6$  A/cm<sup>2</sup> at 77 K in zero magnetic field (Fig.1). The criterion for the critical current density ( $J_c$ ) measurements was 1  $\mu$ V/cm electric field. The magnetic field was applied parallel to the c plane of the superconductor (H//c). The  $J_c$  value of ED Tl-1223 films are comparable to the highest value ever reported for any processing technique, including pulsed-laser deposition, sputtering, and e-beam techniques.<sup>4-6</sup>

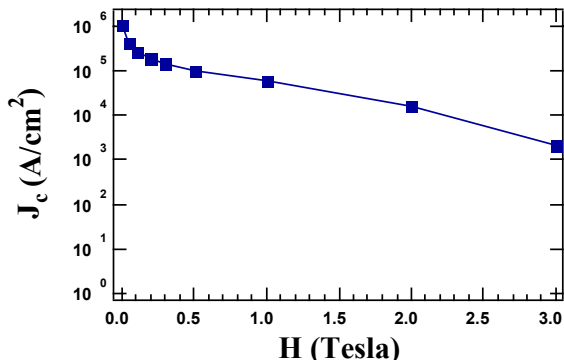


Fig. 1. The magnetic-field dependence of transports  $J_c$  at 77 K (H//c) of an ED-TBSBCCO-Ag film on LAO

In the second part of the paper, electrodeposition and electroless deposition of semiconductor Cu-In-Ga-Se thin films are discussed. Thin-film  $\text{CuIn}_{1-x}\text{Ga}_x\text{Se}_2$  (CIGS)-based solar cells have the highest performance efficiencies in both small-area devices and large-area ( $4000 \text{ cm}^2$ ) modules: 18.8%<sup>7</sup> and 12.1%,<sup>8</sup> respectively. Test modules and arrays based on CIGS-based devices have been operating outdoors for more than 10 years with little degradation.<sup>9</sup> The 18.8%-efficient device prepared in our research laboratory<sup>7</sup> is based on a multistep process using physical vapor deposition (PVD). The PVD technique is challenging to scale up because of film non-uniformity and low material utilization. Sputtering techniques are suitable for large-area deposition; however, they require expensive vacuum equipment and sputtering targets. Therefore, non-

vacuum electrodeposition and electroless deposition (EL) techniques<sup>10,11</sup> with a potential to prepare large-area uniform precursor films using low-cost source materials and low-cost capital equipment are very attractive for the growth of CIGS layers for photovoltaic applications. We have fabricated 15.4%-efficient (Fig.2) and 13.4%-efficient (Fig.3)

$\text{CuIn}_{1-x}\text{Ga}_x\text{Se}_2$  (CIGS)-based devices from electrodeposited and electroless-deposited precursors. As-deposited precursors are Cu-rich films and polycrystalline or amorphous in nature. Additional In, Ga, and Se were added to the precursor films by physical evaporation to adjust the final composition to  $\text{CuIn}_{1-x}\text{Ga}_x\text{Se}_2$ . Addition of In and Ga and also selenization at high temperature are crucial to obtain high-efficiency devices. The films/devices have been characterized by ICP spectrometry, Auger electron spectroscopy, X-ray diffraction, electron-probe microanalysis, current-voltage (I-V) characteristics, and spectral response.

The ED and EL deposition processes are simple and fast, and they can synthesize multi-component precursors for subsequent processing into high-quality multinary compounds for energy-related applications.

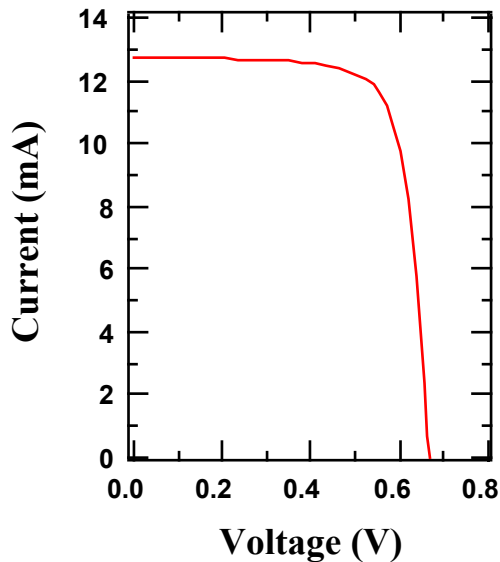


Fig. 2. I-V characteristics of an ED device ( $V_{oc} = 0.666 \text{ V}$ ,  $I_{sc} = 12.76 \text{ mA}$ ,  $J_{sc} = 30.51 \text{ mA/cm}^2$  Fill Factor = 75.56%, Efficiency = 15.4%).

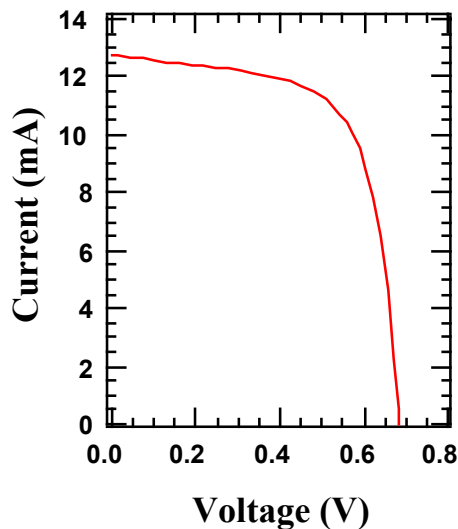


Fig. 3. I-V characteristics of an EL device ( $V_{oc} = 0.6866 \text{ V}$ ,  $I_{sc} = 12.72 \text{ mA}$ ,  $J_{sc} = 29.29 \text{ mA/cm}^2$ , Fill Factor = 66.87%, Efficiency = 13.4%).

## REFERENCES

- [1] R.N. Bhattacharya, R.D. Blaugher, A. Natarajan, C.M. Carlson, P.A. Parilla, D.S. Ginley, M. Paranthaman, A. Goyal, and D.M. Kroeger, *Jour. of Superconductivity*, **11**, 173 (1998).
- [2] T.J. Doi, T. Yuasa, T. Ozawa, and K. Higashiyama, *Jpn. J. Appl. Phys.*, **33**, 5692 (1994).
- [3] A. Goyal, D.P. Norton, J.D. Budai, M. Paranthaman, E.D. Specht, D.M. Kroeger, D.K. Christen, Q. He, B. Saffian, F.A. List, D.F. Lee, P.M. Martin, C.E. Klabunde, E. Hartfield, and V.K. Sikka, *Appl. Phys. Lett.*, **69**, 1795 (1996).
- [4] W.Y. Lee, V. Y. Lee, J. Salem, T.C. Huang, R. Savoy, D.C. Bullock, and S.S.P. Parkin, *Appl. Phys. Lett.*, **53**, 329 (1988).
- [5] Z.F. Ren, C.A. Wang, and J.H. Wang, *Appl. Phys. Lett.*, **65**, 237 (1994).
- [6] R.S. Liu, D.N. Zheng, J.W. Loram, K.A. Mirza, A.M. Campbell, and P.P. Edwards, *Appl. Phys. Lett.*, **60**, 1021 (1992).
- [7] M.A. Contreras, B. Egaas, K. Ramanathan, J. Hiltner, A. Swartzlander, F. Hasoon, and R. Noufi, *Progress in Photovoltaics*, July, (1999).
- [8] F.H. Karg, 11<sup>th</sup> International Photovoltaic Science and Engineering Conference (PVSEC 11), September 20-24, Sapporo City, Hokkaido, Japan, (1999).
- [9] H.S. Ullal, K. Zweibel, and B. von Roedern, *Proc. 26<sup>th</sup> IEEE PVSC*, Anaheim, CA, 301 (1997).
- [10] R.N. Bhattacharya, W. Batchelor, J.F. Hiltner, and J.R. Sites, *Applied Physics Letters*, **75**, No. 10, September, (1999).
- [11] R.N. Bhattacharya, W. Batchelor, H. Wiesner, F. Hasoon, J.E. Granata, K. Ramanathan, J. Alleman, J. Keane, A. Mason, R.J. Matson, and R.N. Noufi, *J. Electrochem. Soc.*, **145**, 3435 (1998).

REPORT DOCUMENTATION PAGE			Form Approved OMB NO. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE December 1999		3. REPORT TYPE AND DATES COVERED Conference Paper
4. TITLE AND SUBTITLE A Low-Cost Approach to Fabrication of Multinary Compounds for Energy-Related Applications				5. FUNDING NUMBERS
6. AUTHOR(S) Raghu N. Bhattacharya and Satyen K. Deb				C TA: PV001501
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)				8. PERFORMING ORGANIZATION REPORT NUMBER
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Renewable Energy Laboratory 1617 Cole Blvd. Golden, CO 80401-3393				10. SPONSORING/MONITORING AGENCY REPORT NUMBER  CP-590-27518
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION/AVAILABILITY STATEMENT National Technical Information Service U.S. Department of Commerce 5285 Port Royal Road Springfield, VA 22161				12b. DISTRIBUTION CODE
13. ABSTRACT (Maximum 200 words) Non-vacuum electrodeposition and electroless deposition techniques with a potential to prepare large-area uniform precursor films using low-cost source materials and low-cost capital equipment are very attractive for the growth of compound materials for superconductors and photovoltaic applications. In the first part, a low-cost electrodeposition (ED) method will be discussed for fabrication of high-temperature Tl-oxide-based superconductors. In the second part, electrodeposition and electroless deposition of semiconductor Cu-In-Ga-Se thin films will be discussed.				
14. SUBJECT TERMS low-cost fabrication; multinary compounds; electrodeposition, electroless deposition; superconductors; photovoltaics				15. NUMBER OF PAGES
				16. PRICE CODE
17. SECURITY CLASSIFICATION OF REPORT Unclassified		18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified		19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified
				20. LIMITATION OF ABSTRACT  UL